

AD-A079 351

AMERICAN UNIV WASHINGTON DC DEPT OF CHEMISTRY

F/B 11/6

THE CHEMICAL NATURE OF ALUMINUM CORROSION. I. ACTIVATION OF ALU--ETC(U)

NOV 79 K SOTOUDEN, R T FOLEY, B F BROWN

N00014-75-C-0799

TR-10

NL

UNCLASSIFIED

[ ]  
AD  
ADDRESS



END  
DATE  
FILMED  
2-80

DOC

ADA 079351


**The Chemical Nature of Aluminum Corrosion:  
I. Activation of Aluminum Surfaces by  
Aluminum Salts**

Technical Report No. 10

Department of Chemistry  
The American University  
Washington, D.C. 20016

By:  
K. Sotoudeh, R.T. Foley and B.F. Brown  
November 1979

To:  
Office of Naval Research  
Contract N00014-75-C-0799  
NR 036-106

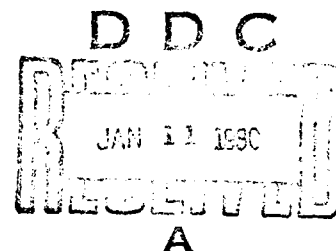

DDC FILE COPY

Reproduction in whole or in part is permitted for any  
purpose of the United States Government.

This work was sponsored by the Metallurgy and  
Ceramics Program of the Office of Naval Research.

80 1-10 019

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM	
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER	
(1) Technical Report No. 10		(9)	
4. TITLE (and Subtitle)		5. TYPE OF REPORT & PERIOD COVERED	
The Chemical Nature of Aluminum Corrosion. I. Activation of Aluminum Surfaces by Aluminum Salts.		Technical Progress Report.	
6. AUTHOR(s)		7. CONTRACT OR GRANT NUMBER(s)	
(10) K. Sotoudeh, R. T. Foley and B. F. Brown		(15) N 00014-75-C-0799 NR 036-106	
8. PERFORMING ORGANIZATION NAME AND ADDRESS		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS	
The American University Massachusetts and Nebraska Avenues, NW Washington, DC 20016			
9. CONTROLLING OFFICE NAME AND ADDRESS		11. REPORT DATE	
Metallurgy and Ceramics Program Office of Naval Research Arlington, VA 22217		(11) November 1979	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		13. NUMBER OF PAGES	
(12) 120		13	
		15. SECURITY CLASS. (of this report)	
		Unclassified	
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report)			
Distribution of this document is unlimited.			
(14) TR-10			
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)			
18. SUPPLEMENTARY NOTES			
19. KEY WORDS (Continue on reverse side if necessary and identify by block number)			
Aluminum, corrosion, pitting, stress corrosion cracking			
20. ABSTRACT (Continue on reverse side if necessary and identify by block number)			
The activation of aluminum surfaces (alloys 1199-H14 and 7075-T6) by solutions of $Al(NO_3)_3$ , $AlBr_3$ , $AlCl_3$ , $Al_2(SO_4)_3$ , $Al(ClO_4)_3$ , $AlI_3$ and $NaCl$ of various concentrations has been measured. Experiments were also conducted in saturated solutions of aluminum acetate, benzoate, phosphate, chromate and fluoride. The dissolution rate of the alloys varies considerably with the salt, the nitrate and iodide being most aggressive. The corrosion rate in sulfate solutions is much less than the rate in bromide, chloride, or perchlorate. The pH of the various salt solutions is not the determining parameter but for a given salt			


DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE

Unclassified 387562  
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

20. (AlCl<sub>3</sub>) the corrosion rate increases with decrease in pH. The experiments definitely demonstrate that the activation effect is not restricted to aluminum chloride and suggests a strong chemical effect in the pitting and stress cracking mechanism. ↙

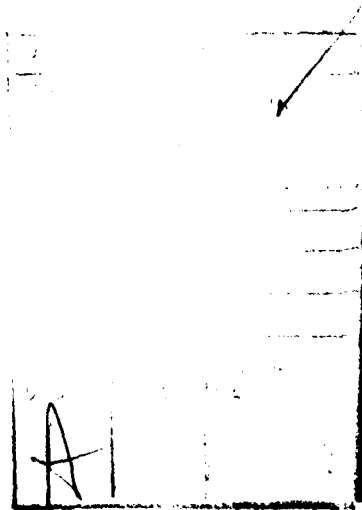

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

THE CHEMICAL NATURE OF ALUMINUM CORROSION: I ACTIVATION  
OF ALUMINUM SURFACES BY ALUMINUM SALTS

K. Sotoudeh, R. T. Foley and B. F. Brown

Department of Chemistry  
The American University  
Washington, D.C. 20016

Aluminum and its alloys are passive unless they are made active by either chemical environments or mechanical actions or by a combination of the two. Although water vapor has been shown in laboratory experiments to be capable of propagating stress corrosion cracks (which indicates a locally active state), it is known from both service experience and laboratory experiments on stress corrosion cracking (to be reported subsequently in this series) that there are effects involving ions other than those of water. It is also known from laboratory experiments that the corrodent in localized forms of corrosion (such as pitting and stress corrosion cracking) is chemically different from the bulk environment, though whether this change is a cause or rather a result of the localized corrosion has not been established.

It is generally recognized that the pH of the solution in a growing pit on an aluminum alloy or in a crack on a stress-cracking specimen of an aluminum alloy is approximately 3.5 and there appears to be a relatively high concentration of  $\text{Al}^{+++}$ . Experiments by Rosenfeld and Marshakov<sup>1</sup>, Brown, et al.<sup>2</sup>, Marek, et al.<sup>3</sup>, Davis<sup>4</sup>, and Hagyard and Santhiapillai<sup>5</sup> support this conclusion. The analytical studies on the nature of local corrodents by Brown, et al., by Marek, et al. and by Davis were conducted on small quantities of corrodent, with attendant uncertainties, and they involved only chloride as

an anion (other than  $\text{OH}^-$ ). Indeed, most of the experimental work in this field has been done in chloride solution and thus an attempt has been made to relate this corrosion to the hydrolysis of aluminum chloride. Almost without exception the thinking has been focused on aluminum chloride and as a result a complete understanding of the pitting mechanism or the stress cracking mechanism has not been realized. The fact is that, aluminum pits and cracks in a number of (non-chloride) environments.

The objective of this work was to measure the corrosion rate of aluminum alloy 1199 and alloy 7075 in various aluminum salt solutions to determine the ability of these various salts to activate the aluminum surface. The longer range intent is to relate this specific corrosion reaction to the initiation of pitting and the stress cracking process.

#### EXPERIMENTAL

The experimental work reported here consisted of immersion tests with two aluminum alloys, alloy 1199-H14 and alloy 7075-T6. Samples  $38 \times 26 \times 0.81$  mm were cleaned in the conventional manner. The strip was immersed in NaOH solution (5g/100ml) at  $70^\circ\text{--}80^\circ\text{C}$  for one minute, rinsed thoroughly, dipped in  $\text{HNO}_3$  (1:3) for one minute at room temperature, and thoroughly rinsed in distilled water and acetone. Samples were immersed in triplicate in solutions of  $\text{Al}(\text{NO}_3)_3$ ,  $\text{AlBr}_3$ ,  $\text{AlCl}_3$ ,  $\text{Al}_2(\text{SO}_4)_3$ ,  $\text{Al}(\text{ClO}_4)_3$ ,  $\text{AlI}_3$  and NaCl of various concentrations as well as in saturated solutions of aluminum acetate, aluminum benzoate, aluminum phosphate, aluminum chromate and aluminum fluoride. These samples were immersed for 7 to 9 day periods at room temperature,  $23^\circ \pm 2^\circ\text{C}$ . Following exposures, the corrosion products were removed with a stripping solution of 20 g of chromic acid and 32.25 ml of 85% phosphoric acid/liter. The weight loss reported was the difference

in weight of the sample before the test and that after the stripping. The latter was corrected with the weight loss of an uncorroded metal specimen in the stripping solution.

## RESULTS

The weight losses for alloy 1199 immersed in 0.1M solutions of aluminum nitrate, bromide, chloride, sulfate, perchlorate and iodide are given in Table I. The activating effect of the nitrate and iodide is approximately three times that of the bromide, chloride and perchlorate, the sulfate one-half. This order is approximately followed in 0.2N solutions in a 7-day experiment reported in Table II. In neither set of experiments is there a correlation between corrosion rate and pH. The pH of these solutions fell in the 3.0-4.0 range with the exception of the aluminum perchlorate solution which had a pH of 2.6-2.7.

Dissolution rates for alloy 7075 in 0.5M solutions of the salts (Table III) were appreciably higher. Aluminum iodide produced a very high corrosion rate as did the nitrate and chloride solutions. The bromide and perchlorate effects were about one-third of the latter and the sulfate solution an order of magnitude lower. Again, the pH of the solution was not a significant factor.

A number of aluminum salts, mainly those formed from weak acids, were used as saturated solutions. These included aluminum acetate, benzoate, phosphate, chromate, and fluoride.

The weight losses exhibited by samples of 1199 in these saturated solutions over a 7 to 9 day period are tabulated in Table IV. Chromate and phosphate solutions gave very little corrosion but the acetate and benzoate gave low but appreciable corrosion rates. The coupons immersed in aluminum

TABLE I

WEIGHT LOSS OF ALUMINUM ALLOY 1199 IN 0.1M SOLUTIONS  
OF VARIOUS ALUMINUM SALT SOLUTIONS

Solution	Duration of Test (days)	pH	Loss in Weight Average (mg/cm <sup>2</sup> )
$\text{Al}(\text{NO}_3)_3$	7	3.30	1.69
	8	3.33	1.22
$\text{AlBr}_3$	7	3.76	0.60
	9	3.64	0.79
$\text{AlCl}_3$	7	3.23	0.58
	9	3.28	0.80
$\text{Al}_2(\text{SO}_4)_3$	7	3.40	0.33
	8	3.28	0.42
$\text{Al}(\text{ClO}_4)_3$	7	2.60	0.60
	9	2.60	0.72
$\text{AlI}_3$	7	3.62	1.83



TABLE II

WEIGHT LOSS OF ALUMINUM ALLOY 1199 IN 0.2N SOLUTIONS  
OF VARIOUS ALUMINUM SALTS

Solution	Duration of Test (days)	pH	Loss in Weight Average (mg/cm <sup>2</sup> )
$\text{Al}(\text{NO}_3)_3$	7	3.32	1.79
$\text{AlBr}_3$	7	3.68	0.74
$\text{AlCl}_3$	7	3.26	0.53
$\text{Al}_2(\text{SO}_4)_3$	7	3.46	0.27
$\text{Al}(\text{ClO}_4)_3$	7	2.70	0.65
$\text{AlI}_3$	7	3.77	1.16

TABLE III

WEIGHT LOSS OF ALUMINUM ALLOY 7075 IN 0.5M SOLUTIONS  
OF ALUMINUM SALTS

Solution	Duration of Test (days)	pH	Loss in Weight Average (mg/cm <sup>2</sup> )
Al(NO <sub>3</sub> ) <sub>3</sub>	7	2.63	10.6
	7	2.60	11.2
AlBr <sub>3</sub>	7	3.36	3.04
	10	2.94	7.07
AlCl <sub>3</sub>	7	2.66	9.69
	7	2.53	9.66
Al <sub>2</sub> (SO <sub>4</sub> ) <sub>3</sub>	7	2.90	0.83
	7	2.81	0.97
Al(ClO <sub>4</sub> ) <sub>3</sub>	7	1.32	3.17
	7	1.10	4.82
AlI <sub>3</sub>	7	3.49	44.9
	7	3.30	51.6

TABLE IV

WEIGHT LOSS OF ALUMINUM ALLOY 1199 IN SATURATED  
SOLUTIONS OF VARIOUS ALUMINUM SALTS

Solution	Duration of Test (days)	pH	Loss in Weight Average (mg/cm <sup>2</sup> )
Al(CH <sub>3</sub> COO) <sub>3</sub>	7	4.78	0.22
	9	4.92	0.10
	7	4.53	0.16
Al(C <sub>6</sub> H <sub>5</sub> COO) <sub>3</sub>	7	3.32	0.15
	9	3.31	0.17
	7	3.54	0.17
Al PO <sub>4</sub>	7	3.00	0.07
	8	2.84	0.09
	7	3.39	0.01
Al(CrO <sub>4</sub> ) <sub>3</sub>	7	3.49	0.005
	8	3.12	0.03
	7	3.37	0.005
AlF <sub>3</sub>	7	5.30	(+0.22)
	8	5.05	(+0.23)
	7	5.22	(+0.56)

fluoride solution gave a weight increase indicating that the standard stripping solution did not remove the precipitated corrosion product. Again, there was no correlation between the corrosion rate and pH of the solution. Similar results were obtained with alloy 7075 (Table V), with the exception that the rate in aluminum acetate solution at a pH, 4.7-4.9, was higher than the other solutions.

For a single salt, aluminum chloride, initially at 0.5N concentration, the corrosion rate varies with pH. This effect is shown in Table VI wherein the dissolution rate drops appreciably in going from a pH of 2.0 to 4.5.

The unexpected results obtained with aluminum nitrate, chloride, and sulfate suggested performing experiments wherein the salts were compared at approximately equivalent activity. The comparison, of necessity, was rather rough because the activity coefficients for these salts over a range of concentrations, particularly in dilute solutions, are not available. To approximate equivalent activities, solutions 0.69M in  $Al_2(SO_4)_3$ , 0.014M in  $AlCl_3$ , and 0.020M in  $AlNO_3$  were compared. However, the order of activation was still the same for the three salts (Table VII).

## DISCUSSION

The idea that aluminum surfaces may be activated by aluminum chloride has been advanced by several other investigators. The "autocatalytic" nature of aluminum pitting seems to have been first suggested by Edeleanu and Evans<sup>6</sup> but explored in more detail by Hagyard and Santhipillai<sup>5</sup>. The latter investigators measured the pH and electrode potential inside an artificial pit on an aluminum electrode undergoing corrosion by short circuit to a graphite cathode in a solution 0.0141M in chloride. The pH in the artificial pit ranged from a minimum of 3.18 to 3.8. The  $AlCl_3$  concen-

TABLE V

WEIGHT LOSS OF ALUMINUM ALLOY IN 7075 IN SATURATED  
SOLUTIONS OF VARIOUS ALUMINUM SALTS

Solution	Duration of Test (days)	pH	Loss in Weight Average (mg/cm <sup>2</sup> )
Al(CH <sub>3</sub> COO) <sub>3</sub>	7	4.67	0.54
	10	4.92	0.42
Al(C <sub>6</sub> H <sub>5</sub> COO) <sub>3</sub>	7	3.40	0.13
	10	3.13	0.26
AlPO <sub>4</sub>	7	3.11	0.075
	7	2.84	0.11
Al(CrO <sub>4</sub> ) <sub>3</sub>	7	3.52	0.005
	7	3.12	0.005
AlF <sub>3</sub>	7	4.90	(0.25)
	7		(0.24)

TABLE VI

WEIGHT LOSS OF ALUMINUM ALLOY 1199 in 0.5N SOLUTION  
OF  $\text{AlCl}_3$  AT DIFFERENT pH's

pH	Duration of Test (days)	Loss in Weight, Average ( $\text{mg}/\text{cm}^2$ )
2.0	7	0.64
3.0	7	0.49
3.5	7	0.46
4.0	7	0.34
4.5	7	0.24

TABLE VII

WEIGHT LOSS OF ALUMINUM ALLOY 1199 IN SOLUTIONS OF  
APPROXIMATELY EQUIVALENT ACTIVITY

Solution	Duration of Test (days)	Molarity	Loss in Weight, Average (mg/cm <sup>2</sup> )
$\text{Al}_2(\text{SO}_4)_3$	7	0.69	0.20
$\text{AlCl}_3$	7	0.014	0.68
$\text{Al}(\text{NO}_3)_3$	7	0.020	0.85

tration at a pH of 3.2 conforms to 0.24 eq/l  $\text{AlCl}_3$ . They concluded that a NaCl solution did not activate the Al surface but highly basic  $\text{AlCl}_3$  at the same pH (3.79) did. Solutions of  $\text{AlCl}_3$  in concentrations of 0.1 and 1.0 eq/l activated Al in times decreasing with increased concentration while NaCl solutions at the same pH did not. Thus the "autocatalytic" nature of the process is not due to the pH or the  $\text{Cl}^-$  but the ability of the  $\text{AlCl}_3$  solution to react with the oxide. The activation can be followed by the potential going negative, e.g. to -0.65 to -0.69 v (vs. Ag-AgCl reference) and the negative potential is due to the Al- $\text{AlCl}_3$  couple.

The present results support the concept that it is the nature of the aluminum salt rather than the pH of the solution produced by the hydrolysis of the aluminum cation. Thus, consistently aluminum sulfate solutions are non-corrosive and aluminum nitrate solutions accelerate corrosion. The results of these experiments emphasize the chemical nature of the process as opposed to strictly physical or electrochemical approaches. The results are inconsistent with some of the mechanisms proposed in the past particularly these that give to the chloride ion unique properties of adsorption and penetration of the oxide film.<sup>7</sup>

This approach is also inconsistent with those models that put a heavy emphasis on flaws and dislocations in the film.<sup>8</sup> Presumably, all of the samples of a given alloy would have the same surface structure.

These experiments definitely demonstrate that aluminum salts in the 3.0-4.0 pH range are accelerators for aluminum corrosion. This effect is not restricted to aluminum chloride solutions. Whether or not they are the accelerators for aluminum pitting and aluminum stress cracking for these processes occurring in neutral salt solutions remains to be demonstrated.



## REFERENCES

1. I.L. Rosenfeld and I.K. Marshakov, *Corrosion* 20, 115t-124t (1964).
2. B.F. Brown, C.T. Fujii and E.P. Dahlberg, *J. Electrochem. Soc.*, 116, 218 (1969).
3. M. Marek, J.G. Rinker and R.F. Hochman, "Solution Chemistry in Crevices and Stress Corrosion Cracks," Presented at Sixth International Congress on Metallic Corrosion, Sydney, Australia, December 3-9, 1975.
4. J.A. Davis in "Localized Corrosion," pp. 168-172, ed. by R.W. Staehle, B.F. Brown, J. Kruger and A. Agrawal, National Association of Corrosion Engineers, Houston, Texas (1974).
5. T. Hagyard and J.R. Santhiapillai, *J. Appl. Chem.*, 9, 323-330 (1959).
6. C. Edeleanu and U.R. Evans, *Trans. Faraday Soc.*, 47, 1121 (1951).
7. H. Kaesche in "Localized Corrosion," ed. by R.W. Staehle, B.F. Brown, J. Kruger and A. Agrawal, pg. 516, National Association of Corrosion Engineers, Houston, Texas (1974).
8. M.J. Pryor, *Z. für Elektrochemie*, 62, 782 (1958).
9. J.A. Richardson and G.C. Wood, *Corrosion Sci.*, 10, 313 (1970).

## DISTRIBUTION LIST

### Organization

Defense Documentation Center  
Cameron Station  
Alexandria, VA 22314

Office of Naval Research  
Department of the Navy  
800 N. Quincy Street  
Arlington, VA 22217

ATTN: Code 471  
Code 102  
Code 470

Commanding Officer  
Office of Naval Research  
Branch Office  
Building 114, Section D  
666 Summer Street  
Boston, MA 02210

Commanding Officer  
Office of Naval Research  
Branch Office  
536 South Clark Street  
Chicago, IL 60605

Office of Naval Research  
San Francisco Area Office  
One Hallidie Plaza Suite 601  
San Francisco, CA 94102

Naval Research Laboratory  
Washington, DC 20375

ATTN: Codes 6000  
6100  
6300  
6400  
2627

Naval Air Development Center  
Code 382  
Warminster, PA 18964  
ATTN: Mr. F. S. Williams

### Organization

Naval Air Propulsion Test Center  
Trenton, NJ 08628  
ATTN: Library

Naval Construction Battalion  
Civil Engineering Laboratory  
Port Hueneme, CA 93043  
ATTN: Materials Division

Naval Electronics Laboratory  
San Diego, CA 92152  
ATTN: Electron Materials  
Sciences Division

Naval Missile Center  
Materials Consultant  
Code 3312-1  
Point Mugu, CA 92041

Commanding Officer  
Naval Surface Weapons Center  
White Oak Laboratory  
Silver Spring, MD 20910  
ATTN: Library

David W. Taylor Naval Ship  
Research and Development Center  
Materials Department  
Annapolis, MD 21402

Naval Undersea Center  
San Diego, CA 92132  
ATTN: Library

Naval Underwater System Center  
Newport, RI 02840  
ATTN: Library

Naval Weapons Center  
China Lake, CA 93555  
ATTN: Library

Naval Postgraduate School  
Monterey, CA 93940  
ATTN: Mechanical Engineering  
Department

Organization

Naval Air Systems Command  
Washington, DC 20360  
ATTN: Codes 52031  
52032

Naval Sea System Command  
Washington, DC 20362  
ATTN: Code 035

Naval Facilities Engineering  
Command  
Alexandria, VA 22331  
ATTN: Code 03

Scientific Advisor  
Commandant of the Marine Corps  
Washington, DC 20380  
ATTN: Code AX

Naval Ship Engineering Center  
Department of the Navy  
Washington, DC 20360  
ATTN: Code 6101

Army Research Office  
P.O. Box 12211  
Triangle Park, NC 27709  
ATTN: Metallurgy & Ceramics Program

Army Materials and Mechanics  
Research Center  
Watertown, MA 02172  
ATTN: Research Programs Office

Air Force Office of Scientific  
Research  
Bldg. 410  
Bolling Air Force Base  
Washington, DC 20332  
ATTN: Chemical Science Directorate  
Electronics & Solid State  
Sciences Directorate

Air Force Materials Laboratory  
Wright-Patterson AFB  
Dayton, OH 45433

Library  
Building 50, Rm 134  
Lawrence Radiation Laboratory  
Berkeley, CA

Organization

NASA Headquarters  
Washington, DC 20546  
ATTN: Code RRM

NASA  
Lewis Research Center  
21000 Brookpark Road  
Cleveland, OH 44135  
ATTN: Library

National Bureau of Standards  
Washington, DC 20234  
ATTN: Metallurgy Division  
Inorganic Materials Div.

Director Applied Physics Laboratory  
University of Washington  
1013 Northeast Fortieth Street  
Seattle, WA 98105

Defense Metals and Ceramics  
Information Center  
Battelle Memorial Institute  
505 King Avenue  
Columbus, OH 43201

Metals and Ceramics Division  
Oak Ridge National Laboratory  
P.O. Box X  
Oak Ridge, TN 37380

Los Alamos Scientific Laboratory  
P.O. Box 1663  
Los Alamos, NM 87544  
ATTN: Report Librarian

Argonne National Laboratory  
Metallurgy Division  
P.O. Box 229  
Lemont, IL 60439

Brookhaven National Laboratory  
Technical Information Division  
Upton, Long Island  
New York 11973  
ATTN: Research Library

Office of Naval Research  
Branch Office  
1030 East Green Street  
Pasadena, CA 91106

Dr. T. R. Beck  
Electrochemical Technology Corporation  
10035 31st Avenue, NE  
Seattle, Washington 98125

Professor I. M. Bernstein  
Carnegie-Mellon University  
Schenley Park  
Pittsburgh, Pennsylvania 15213

Professor H. K. Birnbaum  
University of Illinois  
Department of Metallurgy  
Urbana, Illinois 61801

Dr. Otto Buck  
Rockwell International  
1049 Camino Dos Rios  
P. O. Box 1085  
Thousand Oaks, California 91360

Dr. David L. Davidson  
Southwest Research Institute  
8500 Culebra Road  
P. O. Drawer 28510  
San Antonio, Texas 78234

Dr. D. J. Duquette  
Department of Metallurgical Engineering  
Rensselaer Polytechnic Institute  
Troy, New York 12181

Professor R. T. Foley  
The American University  
Department of Chemistry  
Washington, D. C. 20016

Mr. G. A. Gehring  
Ocean City Research Corporation  
Tennessee Avenue & Beach Thorofare  
Ocean City, New Jersey 08226

Dr. J. A. S. Green  
Martin Marietta Corporation  
1450 South Rolling Road  
Baltimore, Maryland 21227

Professor R. H. Heidersbach  
University of Rhode Island  
Department of Ocean Engineering  
Kingston, Rhode Island 02881

Professor H. Herman  
State University of New York  
Material Sciences Division  
Stony Brook, New York 11970

Professor J. P. Hirth  
Ohio State University  
Metallurgical Engineering  
1314 Kinnear Road  
Columbus, Ohio 43212

Dr. E. W. Johnson  
Westinghouse Electric Corporation  
Research and Development Center  
1310 Beulah Road  
Pittsburgh, Pennsylvania 15235

Professor R. M. Latanision  
Massachusetts Institute of Technology  
77 Massachusetts Avenue  
Room E19-702  
Cambridge, Massachusetts 02139

Dr. F. Mansfeld  
Rockwell International Science Center  
1049 Camino Dos Rios  
P. O. Box 1085  
Thousand Oaks, California 91360

Dr. Jeff Perkins  
Naval Postgraduate School  
Monterey, California 93940

Professor H. W. Pickering  
Pennsylvania State University  
Department of Material Sciences  
University Park, Pennsylvania 16802

Dr. E. A. Starke, Jr.  
Georgia Institute of Technology  
School of Chemical Engineering  
Atlanta, Georgia 30332

Dr. Barry C. Syrett  
Stanford Research Institute  
333 Ravenswood Avenue  
Menlo Park, California 94025

Dr. R. P. Wei  
Lehigh University  
Institute for Fracture and  
Solid Mechanics  
Bethlehem, Pennsylvania 18015

Professor H. G. F. Wilsdorf  
University of Virginia  
Department of Materials Science  
Charlottesville, Virginia 22903

Dr. Clive Clayton  
State University of New York  
Material Sciences Division  
Stony Brook, New York 11970